

Biomedical applications of copper nanoparticles: an up-to-date overview

Negin Khosravi^a, Alaa Alzufairi^b, Parisa Zahed^c, Aliasghar Abouchenari^d, Sohrab Asgaran^e, Setareh Reza-Soltani^f, Zahra Moazzami Goudarzi^{g*}

^a School of Science and Health, The University of Georgia, Tbilisi, Georgia

^b Department of Medical Laboratory Sciences, Faculty of Allied Health Sciences, Kuwait University, Kuwait

^c Iran University of Medical Sciences, Finetech in Medicine Research Center, Iran University of Medical Sciences, Tehran, Iran.

^d Materials Engineering, Shahid Bahonar University, Kerman, Iran

^e Helmaco Sp. Z o.o. Company, Ostrobramska 101 / 335K, 04-041 Warsaw, Poland

^f Advanced Diagnostic and Interventional Radiology Research Center (ADIR), Tehran University of Medical Science (TUMS), Tehran, Iran

⁸ Laboratory of Polymers and Biomaterials, Institute of Fundamental Technological Research, Polish Academy of Sciences, Pawinskiego 5B, Warsaw, 02–106 Poland

ABSTRACT

Copper nanoparticles (CuNPs) have garnered significant attention in biomedicine due to their various properties and potential applications. These nanoparticles exhibit promising antimicrobial, anticancer, and antioxidant activities, which enhance their value in nanomedicine applications. Their properties, shaped by the fabrication techniques, facilitate their application in drug delivery, cancer therapy, tissue engineering, and dental applications uses. Nevertheless, obstacles persist in attaining biocompatibility and regulated release, which are vital for effective clinical transference. Toxicological evaluations are essential to ensure the secure utilization of CuNPs. Additionally, studies are ongoing to find creative solutions to address these challenges and fully harness the medical potential of CuNPs.

©2024 UGPH.

Peer review under responsibility of UGPH.

1. Introduction

When nanotechnology first emerged, it transformed several industries, most notably healthcare, where the unique properties of nanoparticles were utilized in innovative ways [1-3]. Copper nanoparticles (CuNPs) have attracted significant attention due to their numerous applications in drug delivery, wound healing, cancer treatment [4]. CuNPs is an excellent choice for various biomedical applications because of its intrinsic qualities, including biocompatibility and antibacterial effectiveness [5]. As antibiotic resistance becomes an increasing concern, recent studies have demonstrated that CuNPs exhibit potent antibacterial activity

ARTICLEINFORMATION

Article History: Received 11 September 2024 Received in Revised from 15 November 2024 Accepted 23 December 2024

Keywords:

Copper nanoparticles Antibacterial Synthesis Biocompatibility Biomedical applications

against various pathogens, including bacteria and fungi [6, 7]. Among these, the synthesis of copper nanoparticles has evolved, with green synthesis methods gaining popularity for being costeffective and environmentally sustainable [8]. Producing CuNPs using plant extracts preserves their therapeutic biocompatibility, making them suitable for medical applications [9]. CuNPs are superior to conventional antibacterial agents due to their large surface area-to-volume ratio, enhancing their reactivity and antimicrobial effectiveness [10]. CuNPs have been investigated for their potential use in tissue engineering and regenerative medicine and their antibacterial qualities. CuNPs may aid tissue regeneration and repair because they stimulate angiogenesis and improve wound healing processes [11]. CuNPs may be added to biomaterials for implants and prostheses to increase their functional performance and biocompatibility, which would benefit patients [12]. Furthermore, CuNPs' adaptability goes beyond only their antibacterial qualities. They have been investigated for use in biosensing technologies, where their localized surface plasmon resonance (SPR) may be adjusted to detect different biomolecules with greater sensitivity and specificity [13, 14]. As research continues to disclose the numerous possibilities of copper nanoparticles in biomedicine, it is vital to solve the problems connected with their utilization. To guarantee the safe and efficient use of CuNPs in clinical settings, issues with toxicity, environmental impact, and the requirement for standardized synthesis processes must be carefully considered [12].

A comprehensive understanding of copper's toxicity mechanisms and cell-affecting effects is essential, given the metal's recent widespread use and research. This study aims to provide a comprehensive overview of the state of copper nanoparticle research, focusing on potential future directions and biological applications.

2. Synthesis and properties copper nanoparticles

Several methods exist to create copper nanoparticles, including physical, chemical, and green synthesis techniques. The following sections will cover all of these methods. Methods and properties of CuNPs is shown in Table 1.

2.1. Physical methods

Physical getting techniques are less common than chemical or environmentally friendly procedures due to their drawbacks, which include the need for costly equipment and considerable energy consumption [15].

The reduction of metal ions in solution (chemical reduction method) is the primary chemical technique for creating metal nanoparticles due to its ease of usage [16]. Because it is easy to use, has a high production efficiency, and requires little equipment, the chemical reduction technique is frequently employed to produce CuNPs. Chemical-reducing agents are used in chemical reduction, as the name suggests. There are several options for their production because this technique may be further categorized based on the energy source or reaction device [17]. The usage of hazardous compounds during the synthesis stage is one significant disadvantage. The development of environmentally friendly procedures is crucial, given the growing use of nanoparticles and their increased interaction with humans [18]. Surface-active microarrays formed by immiscible water-oil, oil-water, and water supercritical carbon dioxide are used in the microemulsion reduction process, also known as colloidal synthesis [19]. Ultrasonic waves with a frequency of around 20 kHz to 10 MHz are the basis of sonochemical reduction; acoustic cavitation, a physical phenomenon, drives the reaction [20]. Cu NPs may now be produced with consistent particle size and shape using hydrothermal treatment and microwaves [21]. The electromagnetic energy used in microwave technology has frequencies between 300 MHz and 300 GHz [22].

2.2. Chemical methods

Compared to chemical synthesis, physical synthesis produces nanoparticles with homogeneous distribution and no solvent contamination [23]. Unconventional physical procedures, including those requiring vacuum or plasma, can occasionally produce lowquality nanoparticles. In order to remove or extract atoms from a bulk surface by emitting a laser beam, a number of physical approaches are used before or after a chemical process. For instance, laser ablation necessitates a colloidal solution, which reduces the possibility of oxidation on the nanoparticles' surface and must be put in a vacuum chamber. This method is not practical because of the intricacy of the apparatus and the high energy required for the laser [24]. Two crucial factors in determining the particle size are the duration of exposure and the quantity of laser beam pulses used. In contrast to previous physical methods, the ions are implanted on a solid substrate using a pulsed electrical current in the Pulsed Wire Discharge (PWD) process [25]. Physical getting techniques are less common than chemical or environmentally friendly procedures due to their drawbacks, which include the need for costly equipment and considerable energy consumption [26].

2.3. Green synthesis

Green synthesis is often used as a safe method for producing metallic nanoparticles. This technique utilizes reducing agent molecules present in microorganisms, such as fungi and bacteria, as well as in plants [27]. Compared to chemical synthesis, it is less expensive, simpler, faster, and more sustainable. It also uses more environmentally acceptable resources. Given the incredible difficulty in maintaining cell cultures, it is preferred to employ plant extracts rather than microorganisms to produce nanoparticles [28]. The biomolecules found in plants, including proteins, amino acids, vitamins, alkaloids, terpenoids, flavones, ketones, aldehydes, tannins, phenolics, saponins, and polysaccharides, are essential for the reduction of metals [29]. Plant biomass is utilized as an extract or as a powder. They are combined with the metal solution of choice. The steps of the synthesis are shown in Fig.1. Common precursor copper salts employed in the production of Cu NPs include copper (II) sulfate pentahydrate (CuSO4.5H₂0), cupric acetate (monohydrate) (CH₃COO) (2Cu·H₂O), copper (II) nitrate (Cu (NO₃)₂), and others. Typically, the extract is combined with a metal salt solution at room temperature and the appropriate pH, either with or without stirring. The synthesis of NPs will be finished in a short period [30, 31].

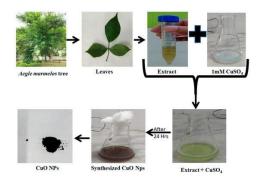


Fig.1. Schematic illustration of the synthesis of CuNPs by plants [32].

Due to their high metal resistance and ease of handling, several fungi have been used for the biogenic production of copper nanoparticles. They produce a range of extracellular enzymes that are crucial to the manufacture of metallic nanoparticles. CuNPs were synthesized using Aspergillus niger because of its capacity to bioaccumulate metals. The common filamentous fungus A. niger has a range of enzymes, including hydrolytic and oxidative enzymes, that allow metal ions to be absorbed from aqueous solutions [33]. Algae are a varied collection of plants being investigated for potential use in nanotechnology. In addition to producing NPs, algae

Table 1

Methods and properties of CuNPs.

are being investigated for their nutritional value, ability to increase bio-diesel, and extensive potential for medicinal use. Compared to chemically manufactured silver nanoparticles, their documented antibacterial action against bacteria recovered from the sick silkworm was found to be more effective, and it is anticipated that they would be biocompatible [34].

3. Biomedical application of copper

Together with other metallic NPs like silver (Ag) [35] and gold (Au) [36], Cu nanoparticle may be used as appealing substitutes in nanomedicine because of their possible antiviral properties, low toxicity, antifungal and antibacterial activity, excellent biocompatibility, oxidation resistance, and better availability at cheaper prices [37]. Table 2 provides information on the characteristics and uses of copper nanoparticles.

3.1. Drug delivery systems

Effectively targeting tissues with therapeutic molecules remains one of the most significant challenges in drug discovery [38, 39]. Copper nanoparticles have gained popularity as drug delivery vehicles due to their vast surface area-to-volume ratio, changeable surface chemistry, and ability to encapsulate a wide range of medications [40]. Several methods, such as surface functionalization, encapsulation in polymeric matrices, and stimuliresponsive drug release procedures, have been used to construct CuNPs-based drug delivery systems [41]. The surface functionalization of CuNPs with targeting ligands, such as peptides or antibodies, enables targeted cell attachment and recognition, increasing the efficacy of drug delivery [42]. According to Assadi et al. [43], CuNPs interacts with antibiotics and functions as a transporter of tetracycline, enhancing its accumulation in bacteria.

Synthesis	Methods	Properties	References
	Thermal decomposition	production of stable nanoparticle and antibacterial activity	[44]
Chemical	Chemical reduction	controlled size and morphology	[15]
	Microwave technique	regular particle size and morphology	[21]
Physical	Evaporation-condensation	small nanoparticles	[23]
		complexity of the equipment	[24]
	Laser beam Aerosol technique	controlled size and morphology	[45]
Green synthesis	Plant and fruit extract mediated	Antimicrobial and antiviral activity	[46, 47]
	Bacterial and fungal-mediated	antimicrobial, antioxidant, and cytotoxic activity	[48]
	Algal mediated	economical, eco-friendly, energy-efficient and less-toxic	[49]

In a different study, Verma et al. [50] produced mupirocin-paired copper nanoparticles to overcome drug resistance in Staphylococcus aureus, which causes dermal skin infections. They found that a gel comprising Mupirocin and Cu NPs was more effective against S. aureus due to its sustained release than a pure drug. Phull et al. [51] synthesized the CuO-Fu-NPs. MTT, TUNEL, and western blot tests showed that the CuO-Fu-NPs could influence apoptosis and growth signaling molecules and had anti-proliferative and genotoxic effects on the cancer cells. The study's findings highlight the importance of using naturally occurring compounds to increase the amount of organic and inorganic metallic nanoparticles in natural product medication development, which may have therapeutic benefits and anticancer drug delivery potential. The anticancer mechanism of the produced fucoidan-capped copper oxide nanoparticles is depicted in Fig.2.

3.2. Cancer therapy

With their many advantages, such as drug stability, appropriate biodistribution, enhanced therapeutic index, and active agent delivery to the precise location (active or passive targeting), copper and copper oxide nanoparticles have attracted much interest in the biomedical domains [52, 53]. Copper-based nanomaterials (Hc-CuO NPs) were created by Chen et al. [54] and comprised of herbal extract of Houttuynia cordata (Hc) and copper oxide (II) nanoparticles, which range in size from 40 to 45 nm. By targeting PI3K/Akt (the phosphatidylinositol 3-kinase/protein kinase B) signaling pathways in cancer cells, the scientists demonstrated that Hc-CuO NPs suppressed the growth of cervical cancer in vitro by overproducing ROS and inducing death. Copper oxide (II) nanoparticles coated with fucoidan from Undaria pinnatifida algae showed genotoxic and antiproliferative effects on HeLa cells, according to Abdelhakm et al. [55].

A potent antibacterial effect is often produced by photothermal treatment, which is directly influenced by particle concentration and laser strength. In Tao et al. [56] study, methacrylate-modified gelatin was used to polymerize CuNPs drastically chelated with N, N-bis(acryloyl)-cystamine (BACA) CuNP proximity resulted in a localized surface plasmon with resonance at 808 nm, creating a three-dimensional network. Depending on the laser intensity and copper concentration, the CuNPs-hydrogel may raise the temperature by up to 40 degrees in 4 minutes at this wavelength.

In a different study, Cabral et al. [57] showed that PL-based hydrogels with CuO NPs or GSNO had a good chance of killing cancer cells. This creates a new therapy option for skin cancer.

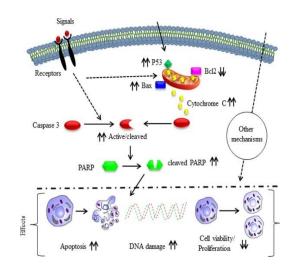


Fig.2. Anticancer mechanism of the synthesized fucoidan-capped copper oxide nanoparticles (CuO-Fu-NPs) [51].

3.3. Tissue engineering

Their exceptional cost-effectiveness justifies the use of copper nanoparticles over other metal nanoparticles [58]. Because copper nanoparticles have antibacterial qualities, using them with fabric softeners is highly advantageous, especially considering the many drawbacks of different fabric softener additions [59].

Incorporating antimicrobial compounds into tissue conditioner structures has been the subject of several attempts. These additions include antibacterial nanoparticles, essential and herbal oils, and antibiotics [60]. Several shortcomings have been noted for the instances under investigation, even though some of these tissue conditioners exhibit encouraging effects against bacteria. The unstable nature of the components supplied to the tissue conditioner and its detrimental impact on its mechanical qualities are two examples of these flaws. There are currently no commercially available antimicrobial tissue conditioners, even though antimicrobial compounds benefit tissue conditioners [61].

Tissue conditioners using copper oxide nanoparticles shown respectable antibacterial activity against E. faecalis, P. aeruginosa, and C. albicans in a study by Nikanjam et al. [59].

Table 2

Properties, applications, and synthesis methods of copper nanoparticle.

Types of Copper Nanoparticles	Methods of Synthesis	Properties	Applications	Reference
CuNPs	Green synthesis (M. oleifera	Improve anti-bacterial and anti-fungal	treatment of various bacterial, and	[62]
	leaves)	activities	particularly, fungal infections	
CuNPs	Green synthesis (Crataegus rose	the relevance of biosafety enhancing the	cancer therapy	[63]
	fruits)	antitumor		
CuONPs	Green synthesis (Melia azedarach	optimizing the uptake and increasing	cancer therapy	[52]
	leaves)	potential of gene therapy		
CuNPs	Green synthesis (musa sapientum	better anti-inflammatory activity and less	anti-inflammatory	[64]
	plant)	biotoxic		
CuNPs	Chemical method	development of antimicrobial agents	Drug delivery	[65]
CuNPs/NGO	Chemical method	outstanding catalytic activity	electrocatalytic activity	[14]
CuO/CuNps	Chemical method	size reduction	biosensor applications	[13]
CuO/AgNPs	Chemical method	increasing the antibacterial effect up to six	treat infected wounds	[66]
		times		
CuNPs	Green synthesis (S. didymobotrya	better antimicrobial activity against E. coli	Antimicrobial activity	
	methanolic root extract)	and S. aureus		[67]
CuNPs	Chemical and	CuNPs that are prepared using green	antimicrobial activity	[68]
	Green synthesis	synthesis have smaller nanoparticle		
		size		
CuO/NPs	Green synthesis	excellent antifungal activity against C.	antifungal	[69]
		albicans	activity	
CuO/NPs	Chemical method	acceptable antimicrobial effects against E.	Tissue Engineering	
		faecalis, P. aeruginosa, and C. albicans		[59]
CuNPs	Green synthesis (black tea leaves	antibacterial capabilities, environmentally	biomedical applications	[70]
		friendly and cost-effective		
CuNPs	Green synthesis (Nigella sativa	less toxicity properties and antibacterial	therapeutic applications	[71]
	seeds	activity		
	extract)			
CuNPs	Green synthesis (ginger and	antimicrobial properties	anticancer activity	[72]
	garlic)			
CuNPs with	Green synthesis	antimicrobial properties	Dental adhesive	[73]
adhesive resin				

3.4. Dental applications

CuNPs have bio-physiochemical and antibacterial qualities. They enhance the material pool to reduce the scarcity of dental materials for various clinical applications. Dental metals and alloys, dental cement, dental polymers and resins, and other dental materials are typically made with copper nanoparticles [10]. According to Gomez et al. [74], covering dental implant healing caps with copper nanoparticles prevented the growth of germs and biofilms. However, another study by Liu et al. [75] showed that an implant made of titanium alloy containing copper has anti-infective qualities against oral bacteria. Additionally, they showed that titanium– copper alloy was biocompatible and prevented peri-implant infections. Different research by Torres et al. [76] demonstrated that adding copper nanoparticles to an adhesive enhanced its antibacterial qualities and shear bond strength without causing cytotoxicity.

4. Future perspectives

The research on copper nanoparticles and copper-based nanomaterials has been less comprehensive than other metallic nanoparticles like gold, silver, or platinum [12]. Broad and reliable information on biokinetics and biodistribution is generally lacking, and much less is known about long-term persistence in the environment and body. A logical design of copper-based nanocomposites and nanostructured materials is anticipated to become more critical in several applications, such as topical therapy, antivirals, antimicrobial tissues and surfaces, and cancer. The studies included in this review emphasize that copper is only harmful when it is more than what the body can process. Substantial control over the quantity of copper injected or discharged is essential to reducing the negative consequences. In order to maintain an adequate amount of copper for effective antibacterial action while preventing an overload, slow-releasing NPs may be crucial [77].

On the other hand, difficulties and safety issues might be a significant worry. Another challenge is developing reproducible and scalable synthesis methods for producing copper nanoparticles in an ecologically responsible manner. Even though a number of green synthesis techniques have been reported in the literature, producing consistent nanoparticle sizes, shapes, and dispersibility remains highly challenging [78]. In conclusion, despite the tremendous progress made in the last few decades in comprehending how Cu surfaces and NPs affect microbes, there are still a lot of unresolved issues about their antimicrobial properties [79].

5. Conclusion

Research on CuNPs for biomedical applications shows their significant potential in various therapeutic fields, including wound healing, antibacterial treatments, and cancer therapies. In term of to current research, CuNPs have exceptional antibacterial qualities that enable them to fight various diseases successfully, making them valuable tools for infection control and preventative measures. The unique physicochemical properties of CuNPs facilitate the targeted and controlled release of therapeutic agents, improving treatment effectiveness while reducing systemic toxicity. Their potential as drug delivery vehicles is similarly intriguing. Even though copper nanoparticles have great promise for use in biomedicine, further study is needed to understand the safety and effectiveness concerns fully.

Authors' contribution

Negin Khosravi: Conceptualization, Writing—Original Draft Preparation, Alaa Alzufairi: Investigation, Writing – review & editing, Parisa Zahed: Conceptualization. Writing – original draft, Writing – review & editing, Aliasghar Abouchenari: Writing – original draft, Writing – review & editing, Sohrab Asgaran: Visualization, Writing—Original Draft Preparation, Setareh Reza-Soltani: Writing—Original Draft Preparation, Writing – review & editing, Zahra Moazzami: Writing—Original Draft Preparation, Writing – review & editing.

Declaration of competing interest

The authors declares that he has no competing interests.

Data availability

No data was used for this review.

Funding

None.

REFERENCES

S. Malik, K. Muhammad, Y. Waheed, Nanotechnology: A Revolution in Modern Industry, Molecules, 2023.

S. Bahadori, M. Azimpour, Advancements in Nanoparticle-Supported Laccase Immobilization: Promising Solutions for Water Treatment, Journal of Composites and Compounds 5(16) (2023) 159-178 DOI: 10.61186/jcc.5.3.2.
 J. Varshosaz, Advancements in Nanostructured Drug Delivery Systems: A Commentary on Multifunctional Approaches for Cancer and Inflammatory Disease Treatment, Journal of Composites and Compounds 5(16) (2023) 210-211 DOI: 10.61186/jcc.5.3.7.

^[4] X. Geng, K. Liu, J. Wang, X. Su, Y. Shi, L. Zhao, Preparation of Ultra-Small Copper Nanoparticles-Loaded Self-Healing Hydrogels with Antibacterial, Inflammation-Suppressing and Angiogenesis-Enhancing Properties for Promoting Diabetic Wound Healing, International Journal of Nanomedicine 18(null) (2023) 3339-3358 DOI: 10.2147/IJN.S399933.

^[5] I.V. Fadeeva, B.I. Lazoryak, G.A. Davidova, F.F. Murzakhanov, B.F. Gabbasov, N.V. Petrakova, M. Fosca, S.M. Barinov, G. Vadalà, V. Uskoković, Y. Zheng, J.V. Rau, Antibacterial and cell-friendly copper-substituted tricalcium phosphate ceramics for biomedical implant applications, Materials Science and Engineering: C 129 (2021) 112410 DOI: https://doi.org/10.1016/j.msec.2021.112410.

^[6] M.M. Zangeneh, H. Ghaneialvar, M. Akbaribazm, M. Ghanimatdan, N. Abbasi, S. Goorani, E. Pirabbasi, A. Zangeneh, Novel synthesis of Falcaria vulgaris leaf extract conjugated copper nanoparticles with potent cytotoxicity, antioxidant, antifungal, antibacterial, and cutaneous wound healing activities under in vitro and in vivo condition, Journal of Photochemistry and Photobiology B: Biology 197 (2019) 111556 DOI: https://doi.org/10.1016/j.jphotobiol.2019.111556.

^[7] A. Yaqub, N. Malkani, A. Shabbir, S.A. Ditta, F. Tanvir, S. Ali, M. Naz, S.A.R. Kazmi, R. Ullah, Novel Biosynthesis of Copper Nanoparticles Using Zingiber and Allium sp. with Synergic Effect of Doxycycline for Anticancer and Bactericidal Activity, Current Microbiology 77(9) (2020) 2287-2299 DOI: 10.1007/s00284-020-02058-4.

^[8] I. Ijaz, E. Gilani, A. Nazir, A. Bukhari, Detail review on chemical, physical and green synthesis, classification, characterizations and applications of nanoparticles, Green Chemistry Letters and Reviews 13(3) (2020) 223-245 DOI: 10.1080/17518253.2020.1802517.

^[9] R. Lu, W. Hao, L. Kong, K. Zhao, H. Bai, Z. Liu, A simple method for the synthesis of copper nanoparticles from metastable intermediates, RSC advances 13(21) (2023) 14361-14369 DOI: A simple method for the synthesis of copper nanoparticles from metastable intermediates.

^[10] V.W. Xu, M.Z.I. Nizami, I.X. Yin, O.Y. Yu, C.Y.K. Lung, C.H. Chu, Application of copper nanoparticles in dentistry, Nanomaterials 12(5) (2022) 805 DOI: <u>https://doi.org/10.3390/nano12050805</u>.

^[11] J. Salvo, C. Sandoval, Role of copper nanoparticles in wound healing for chronic wounds: literature review, Burns Trauma 10 (2022) tkab047 DOI: 10.1093/burnst/tkab047.

^[12] M.J. Woźniak-Budych, K. Staszak, M. Staszak, Copper and copper-based nanoparticles in medicine—perspectives and challenges, Molecules 28(18) (2023) 6687 DOI: <u>https://doi.org/10.3390/molecules28186687</u>.

^[13] A. Ramachandran, S. Nair, Tuning of Localized Surface Plasmon Resonance in Copper-Copper Oxide Core-Shell Quantum Dots for the Application in Biosensors, (2020) DOI: https://www.preprints.org/manuscript/202003.0253/v1.

^[14] K. Sivasankar, K.K. Rani, S.-F. Wang, R. Devasenathipathy, C.-H. Lin, Copper nanoparticle and nitrogen doped graphite oxide based biosensor for

the sensitive determination of glucose, Nanomaterials 8(6) (2018) 429 DOI: https://doi.org/10.3390/nano8060429.

[15] H.R. Ghorbani, Chemical synthesis of copper nanoparticles, Oriental Journal of Chemistry 30(2) (2014) 15-18 DOI: http://dx.doi.org/10.13005/ojc/300254.

[16] N. Bisht, P. Phalswal, P.K. Khanna, Selenium nanoparticles: A review on synthesis and biomedical applications, Materials Advances 3(3) (2022) 1415-1431 DOI: <u>https://doi.org/10.1039/D1MA00639H</u>.

[17] G. Suriati, M. Mariatti, A. Azizan, Synthesis of silver nanoparticles by chemical reduction method: Effect of reducing agent and surfactant concentration, International journal of automotive and mechanical engineering 10 (2014) 1920-1927 DOI: https://doi.org/10.15282/ijame.10.2014.9.0160.

[18] H.J. Lee, J.Y. Song, B.S. Kim, Biological synthesis of copper nanoparticles using Magnolia kobus leaf extract and their antibacterial activity, Journal of Chemical Technology & Biotechnology 88(11) (2013) 1971-1977 DOI: <u>https://doi.org/10.1002/jctb.4052</u>.

[19] B. Khodashenas, H.R. Ghorbani, Synthesis of copper nanoparticles: An overview of the various methods, Korean Journal of Chemical Engineering 31 (2014) 1105-1109 DOI: <u>https://doi.org/10.1007/s11814-014-0127-y</u>.

[20] M.H. Mahdieh, B. Fattahi, Effects of water depth and laser pulse numbers on size properties of colloidal nanoparticles prepared by nanosecond pulsed laser ablation in liquid, Optics & Laser Technology 75 (2015) 188-196 DOI: https://doi.org/10.1016/j.optlastec.2015.07.006.

[21] P.V. Quintana-Ramirez, M.C. Arenas-Arrocena, J. Santos-Cruz, M. Vega-González, O. Martínez-Alvarez, V.M. Castaño-Meneses, L.S. Acosta-Torres, J. de la Fuente-Hernández, Growth evolution and phase transition from chalcocite to digenite in nanocrystalline copper sulfide: Morphological, optical and electrical properties, Beilstein journal of nanotechnology 5(1) (2014) 1542-1552 DOI: https://doi.org/10.3762/bjnano.5.166.

[22] M. Blosi, S. Albonetti, M. Dondi, C. Martelli, G. Baldi, Microwaveassisted polyol synthesis of Cu nanoparticles, Journal of Nanoparticle Research 13 (2011) 127-138 DOI: <u>https://doi.org/10.1007/s11051-010-0010-</u>7.

[23] S. Iravani, H. Korbekandi, S.V. Mirmohammadi, B. Zolfaghari, Synthesis of silver nanoparticles: chemical, physical and biological methods, Research in pharmaceutical sciences 9(6) (2014) 385-406.

[24] H.-J. Im, E.C. Jung, Colloidal nanoparticles produced from Cu metal in water by laser ablation and their agglomeration, Radiation Physics and Chemistry 118 (2016) 6-10 DOI: https://doi.org/10.1016/j.radphyschem.2015.06.005.

[25] S. Kojima, Y. Ichino, Y. Yoshida, Improvement of upper critical field in YBa2Cu3Oy films by substituting 3d metal for CU sites using combinatorial pulsed-laser deposition, Physics Procedia 58 (2014) 58-61 DOI: https://doi.org/10.1016/j.phpro.2014.09.015.

[26] M.C. Crisan, M. Teodora, M. Lucian, Copper nanoparticles: Synthesis and characterization, physiology, toxicity and antimicrobial applications, Applied Sciences 12(1) (2021) 141 DOI: https://doi.org/10.3390/app12010141.

[27] S.S. Salem, A. Fouda, Green Synthesis of Metallic Nanoparticles and Their Prospective Biotechnological Applications: an Overview, Biological Trace Element Research 199(1) (2021) 344-370 DOI: 10.1007/s12011-020-02138-3.

[28] M.A. Asghar, M.A. Asghar, Green synthesized and characterized copper nanoparticles using various new plants extracts aggravate microbial cell membrane damage after interaction with lipopolysaccharide, International journal of biological macromolecules 160 (2020) 1168-1176 DOI: https://doi.org/10.1016/j.ijbiomac.2020.05.198.

[29] D. Nath, P. Banerjee, Green nanotechnology–a new hope for medical biology, Environmental toxicology and pharmacology 36(3) (2013) 997-1014 DOI: <u>https://doi.org/10.1016/j.etap.2013.09.002</u>.

[30] C. Ortega-Nieto, N. Losada-Garcia, B.C. Pessela, P. Domingo-Calap, J.M. Palomo, Design and synthesis of copper nanobiomaterials with antimicrobial properties, ACS bio & med Chem Au 3(4) (2023) 349-358 DOI: DOI: 10.9734/JALSI/2020/v23i730172.

[31] M.A. Atiya, A.K. Hassan, I.M. Luaibi, Green synthesis of bimetallic iron/copper nanoparticles using ficus leaves extract for removing orange G (OG) dye from aqueous medium, Nat. Environ. Pollut. Technol 21(1) (2022) 355-365 DOI: DOI: 10.9734/JALSI/2020/v23i730172.

[32] S.G. Ali, U. Haseen, M. Jalal, R.A. Khan, A. Alsalme, H. Ahmad, H.M. Khan, Green synthesis of copper oxide nanoparticles from the leaves of Aegle marmelos and their antimicrobial activity and photocatalytic activities, Molecules 28(22) (2023) 7499 DOI: https://doi.org/10.3390/molecules28227499.

[33] S. Noor, Z. Shah, A. Javed, A. Ali, S.B. Hussain, S. Zafar, H. Ali, S.A. Muhammad, A fungal based synthesis method for copper nanoparticles with the determination of anticancer, antidiabetic and antibacterial activities, Journal of Microbiological Methods 174 (2020) 105966 DOI: https://doi.org/10.1016/j.mimet.2020.105966.

[34] R. Varshney, S. Bhadauria, M.S. Gaur, A review: biological synthesis of silver and copper nanoparticles, Nano Biomedicine & Engineering 4(2) (2012).

[35] S. Ranjbar, A. Bakhtiari, N. Khosravi, S. Jafari Ashkavandi, F. Azamian, M. Alijaniha, M. Karbalaee, Silver Nanoparticles: Biomedical Applications and Future Perspectives, Journal of Composites and Compounds 6(20) (2024).
[36] D.A. Giljohann, D.S. Seferos, W.L. Daniel, M.D. Massich, P.C. Patel, C.A. Mirkin, Gold nanoparticles for biology and medicine, Spherical nucleic acids (2020) 55-90.

[37] L. Wang, Synthetic methods of CuS nanoparticles and their applications for imaging and cancer therapy, RSC advances 6(86) (2016) 82596-82615 DOI: https://doi.org/10.1039/C6RA18355G.

[38] A. Bakhtiari, L. Arabuli, F. Sadeghi, N. Tamimi, J. Hosseinzadeh, A. Jafari Rad, O. Hamlehdari Najafabadi, Smart biomaterial composites for controlled drug release: mechanisms and applications, Journal of Composites and Compounds 5(17) (2023) DOI: 10.61186/jcc.5.4.3.

[39] F. Niazvand, A. Cheshmi, M. Zand, R. NasrAzadani, B. Kumari, A. Raza, S. Nasibi, An overview of the development of composites containing Mg and Zn for drug delivery, Journal of Composites and Compounds 2(5) (2020) 193-204 DOI: 10.29252/jcc.2.4.4.

[40] M. Roshani, A. Rezaian-Isfahni, M.H. Lotfalizadeh, N. Khassafi, M.H.J.N. Abadi, M. Nejati, Metal nanoparticles as a potential technique for the diagnosis and treatment of gastrointestinal cancer: a comprehensive review, Cancer Cell International 23(1) (2023) 280 DOI: https://doi.org/10.1186/s12935-023-03115-1.

[41] P. Singh, Y.-J. Kim, D. Zhang, D.-C. Yang, Biological synthesis of nanoparticles from plants and microorganisms, Trends in biotechnology 34(7) (2016) 588-599.

[42] J. Jeevanandam, A. Barhoum, Y.S. Chan, A. Dufresne, M.K. Danquah, Review on nanoparticles and nanostructured materials: history, sources, toxicity and regulations, Beilstein journal of nanotechnology 9(1) (2018) 1050-1074 DOI: <u>https://doi.org/10.3762/bjnano.9.98</u>.

[43] Z. Assadi, G. Emtiazi, A. Zarrabi, Novel synergistic activities of tetracycline copper oxide nanoparticles integrated into chitosan micro particles for delivery against multiple drug resistant strains: Generation of reactive oxygen species (ROS) and cell death, Journal of drug delivery science and technology 44 (2018) 65-70 DOI: 10.1016/j.jddst.2017.11.017.

[44] A.T. Odularu, Metal nanoparticles: thermal decomposition, biomedicinal applications to cancer treatment, and future perspectives, Bioinorganic chemistry and applications 2018(1) (2018) 9354708 DOI: https://doi.org/10.1155/2018/9354708.

[45] S. Aghajani, A. Accardo, M. Tichem, Aerosol Direct Writing and Thermal Tuning of Copper Nanoparticle Patterns as Surface-Enhanced Raman Scattering Sensors, ACS Applied Nano Materials 3(6) (2020) 5665-5675 DOI: 10.1021/acsanm.0c00887.

[46] P. Yugandhar, T. Vasavi, Y. Jayavardhana Rao, P. Uma Maheswari Devi, G. Narasimha, N. Savithramma, Cost effective, green synthesis of copper oxide nanoparticles using fruit extract of Syzygium alternifolium (Wt.) Walp., characterization and evaluation of antiviral activity, Journal of Cluster Science 29 (2018) 743-755 DOI: https://doi.org/10.1007/s10876-018-1395-1.

[47] S. Kayalvizhi, A. Sengottaiyan, T. Selvankumar, B. Senthilkumar, C. Sudhakar, K. Selvam, Eco-friendly cost-effective approach for synthesis of copper oxide nanoparticles for enhanced photocatalytic performance, Optik 202 (2020) 163507 DOI: <u>https://doi.org/10.1016/j.ijleo.2019.163507</u>.

[48] M. Sriramulu, S. Shanmugam, V.K. Ponnusamy, Agaricus bisporus mediated biosynthesis of copper nanoparticles and its biological effects: An in-vitro study, Colloid and Interface Science Communications 35 (2020) 100254 DOI: <u>https://doi.org/10.1016/j.colcom.2020.100254</u>.

[49] A. Sharma, S. Sharma, K. Sharma, S.P. Chetri, A. Vashishtha, P. Singh, R. Kumar, B. Rathi, V. Agrawal, Algae as crucial organisms in advancing nanotechnology: a systematic review, Journal of applied phycology 28 (2016) 1759-1774 DOI: <u>https://doi.org/10.1007/s10811-015-0715-1</u>.

[50] V. Verma, D. Kaushik, Mupirocin Mounted copper nanoparticle offered augmented drug delivery against resistant bacteria, Indian J. Pharm. Educ. Res 54 (2020) 637-646 DOI: DOI: 10.5530/ijper.54.3.113.

[51] A.-R. Phull, A. Ali, K.R. Dhong, M. Zia, P.G. Mahajan, H.-J. Park, Synthesis, characterization, anticancer activity assessment and apoptosis signaling of fucoidan mediated copper oxide nanoparticles, Arabian Journal of Chemistry 14(8) (2021) 103250 DOI: https://doi.org/10.1016/j.arabjc.2021.103250.

[52] K. Jagaran, M. Singh, Copolymer-green-synthesized copper oxide nanoparticles enhance folate-targeting in cervical cancer cells in vitro, Polymers 15(10) (2023) 2393 DOI: <u>https://doi.org/10.3390/polym15102393</u>.
 [53] M.J. Woźniak-Budych, B. Maciejewska, Ł. Przysiecka, D. Wieczorek, K. Staszak, J. Jenczyk, T. Jesionowski, S. Jurga, Comprehensive study of stability of copper oxide nanoparticles in complex biological media, Journal of Molecular Liquids 319 (2020) 114086 DOI: <u>https://doi.org/10.1016/j.molliq.2020.114086</u>.

[54] H. Chen, X. Feng, L. Gao, S. Mickymaray, A. Paramasivam, F. Abdulaziz Alfaiz, H.A. Almasmoum, M.M. Ghaith, R.A. Almaimani, I.A. Aziz Ibrahim, Inhibiting the PI3K/AKT/mTOR signalling pathway with copper oxide nanoparticles from Houttuynia cordata plant: attenuating the proliferation of cervical cancer cells, Artificial Cells, Nanomedicine, and Biotechnology 49(1) (2021) 240-249.

[55] L.O. Abdelhakm, E.I. Kandil, S.Z. Mansour, S.M. El-Sonbaty, Chrysin encapsulated copper nanoparticles with low dose of gamma radiation elicit tumor cell death through p38 MAPK/NF-κB pathways, Biological Trace Element Research 201(1) (2023) 5278-5297 DOI: https://doi.org/10.1007/s12011-023-03596-1.

[56] B. Tao, C. Lin, Y. Deng, Z. Yuan, X. Shen, M. Chen, Y. He, Z. Peng, Y. Hu, K. Cai, Copper-nanoparticle-embedded hydrogel for killing bacteria and promoting wound healing with photothermal therapy, Journal of Materials Chemistry B 7(15) (2019) 2534-2548 DOI: https://doi.org/10.1039/C8TB03272F.

[57] F.V. Cabral, B.d.M. Santana, C.N. Lange, B.L. Batista, A.B. Seabra, M.S. Ribeiro, Pluronic F-127 hydrogels containing copper oxide nanoparticles and a nitric oxide donor to treat skin cancer, Pharmaceutics 15(7) (2023) 1971 DOI: <u>https://doi.org/10.3390/pharmaceutics15071971</u>.

[58] U. Bogdanović, V. Lazić, V. Vodnik, M. Budimir, Z. Marković, S. Dimitrijević, Copper nanoparticles with high antimicrobial activity, Materials letters 128 (2014) 75-78 DOI: <u>https://doi.org/10.1016/j.matlet.2014.04.106</u>.
[59] S. Nikanjam, A. Yeganegi, M.-Y. Alikhani, A. Farmany, S.A. Ghiasian,

R. Hasanzade, Novel antimicrobial applications of copper oxide nanoparticles after combination with tissue conditioner used in complete prostheses, BMC Oral Health 24(1) (2024) 752 DOI: <u>https://doi.org/10.1186/s12903-024-</u>04534-w.

[60] Z. Iqbal, M.S. Zafar, Role of antifungal medicaments added to tissue conditioners: A systematic review, Journal of prosthodontic research 60(4) (2016) 231-239 DOI: <u>https://doi.org/10.1016/j.jpor.2016.03.006</u>.

[61] S. Fernando, T. Gunasekara, J. Holton, Antimicrobial nanoparticles: applications and mechanisms of action, (2018).

[62] P.E. Das, I.A. Abu-Yousef, A.F. Majdalawieh, S. Narasimhan, P. Poltronieri, Green synthesis of encapsulated copper nanoparticles using a hydroalcoholic extract of Moringa oleifera leaves and assessment of their antioxidant and antimicrobial activities, Molecules 25(3) (2020) 555 DOI: https://doi.org/10.3390/molecules25030555.

[63] G.D. Cab-Torres, L. López, D. Salado-Leza, G. Navarro-Tovar, Harnessing Crataegus Rosei "Tejocote" for Biogenic Synthesis of Copper Nanoparticles and Cytotoxicity in Normal and Cancer Cells, Available at SSRN 5077740 DOI: <u>https://dx.doi.org/10.2139/ssrn.5077740</u>.

[64] R. Akshaya, S.B. Ganesh, S. Rajeshkumar, Anti Inflammatory Activity of Musa Sapientum and Its Mediated Copper Nanoparticles- An In Vitro Study, Journal of Pharmaceutical Research International (2021) DOI: https://doi.org/10.9734/jpri%2F2021%2Fv33i64b35742.

[65] N. Karikalan, Synthesis and charaterization of copper nanoparticles and evaluation of antibacterial activity, Rasayan J Chem 11(4) (2018) 1451-1457 DOI: <u>http://dx.doi.org/10.31788/RJC.2018.1143068</u>.

[66] G. Vasiliev, A.-L. Kubo, H. Vija, A. Kahru, D. Bondar, Y. Karpichev, O. Bondarenko, Synergistic antibacterial effect of copper and silver nanoparticles and their mechanism of action, Scientific Reports 13(1) (2023) 9202.

[67] J.K. Cherutoi, C.M. Achisa, Optimization, characterization, and antibacterial activity of copper nanoparticles synthesized using senna didymobotrya root extract, (2021) DOI: https://doi.org/10.1155/2021/5611434.

[68] A. MM Soliman, E. AM Abdallah, E. E Hafez, E. A Kadous, F. A Kassem, Nematicidal Activity of Chemical and Green Biosynthesis of Copper Nanoparticles Against Root-Knot Nematode, Meloidogyne Incognita, Alexandria Science Exchange Journal 43(4) (2022) 583-591 DOI: https://doi.org/10.21608/asejaiqisae.2022.271961.

[69] L.E. Garcia-Marin, K. Juarez-Moreno, A.R. Vilchis-Nestor, E. Castro-Longoria, Highly antifungal activity of biosynthesized copper oxide nanoparticles against Candida albicans, Nanomaterials 12(21) (2022) 3856 DOI: <u>https://doi.org/10.3390/nano12213856</u>.

[70] R. Saleh, A.H. Gomaa, A.G. Elsayed, A. Daher, Green synthesis of copper nanoparticles: Synthesis, characterization and their application: About future, Egyptian Journal of Chemistry 65(2) (2022) 357-368.

[71] M. Kumar, D. Kaushik, A. Kumar, P. Gupta, C. Proestos, E. Oz, E. Orhan, J. Kaur, M.R. Khan, T. Elobeid, Anti obesity and antibacterial activity of green synthesis of copper nanoparticles by Nigella sativa seeds, International Journal of Food Science & Technology (2023) DOI: https://doi.org/10.1111/ijfs.16359.

[72] A. Yaqub, N. Malkani, A. Shabbir, S.A. Ditta, F. Tanvir, S. Ali, M. Naz, S.A.R. Kazmi, R. Ullah, Novel biosynthesis of copper nanoparticles using Zingiber and Allium sp. with synergic effect of doxycycline for anticancer and bactericidal activity, Current Microbiology 77 (2020) 2287-2299 DOI: https://doi.org/10.1007/s00284-020-02058-4.

[73] M.F. Gutiérrez, P. Malaquias, V. Hass, T.P. Matos, L. Lourenço, A. Reis, A.D. Loguercio, P.V. Farago, The role of copper nanoparticles in an etch-andrinse adhesive on antimicrobial activity, mechanical properties and the durability of resin-dentine interfaces, Journal of dentistry 61 (2017) 12-20 DOI: <u>https://doi.org/10.1016/j.jdent.2017.04.007</u>.

[74] A. Gómez, J. Jofre, E. Perez-Tijerina, S. Sólis-Pomar, G. Sánchez-Sanhueza, M. Meléndrez, Effect of titanium coated with 3 different types of copper nanoparticles in the oral biofilm formation, Journal of Dental Health, Oral Disorders & Therapy 12(1) (2021) 1-6.

[75] H. Liu, Y. Tang, S. Zhang, H. Liu, Z. Wang, Y. Li, X. Wang, L. Ren, K. Yang, L. Qin, Anti-infection mechanism of a novel dental implant made of titanium-copper (TiCu) alloy and its mechanism associated with oral microbiology, Bioactive materials 8 (2022) 381-395.

[76] R. Torres-Rosas, N. Torres-Gómez, R. García-Contreras, R.J. Scougall-Vilchis, L.R. Domínguez-Díaz, L. Argueta-Figueroa, Copper nanoparticles as nanofillers in an adhesive resin system: an in vitro study, Dental and Medical Problems 57(3) (2020) 239-246.

[77] M.L. Ermini, V. Voliani, Antimicrobial nano-agents: the copper age, ACS nano 15(4) (2021) 6008-6029.

[78] E. Mavil-Guerrero, R. Vazquez-Duhalt, K. Juarez-Moreno, Exploring the cytotoxicity mechanisms of copper ions and copper oxide nanoparticles in cells from the excretory system, Chemosphere 347 (2024) 140713 DOI: doi.org/10.1016/j.chemosphere.2023.140713.

[79] J. Ramos-Zúñiga, N. Bruna, J.M. Pérez-Donoso, Toxicity mechanisms of copper nanoparticles and copper surfaces on bacterial cells and viruses, International Journal of Molecular Sciences 24(13) (2023) 10503 DOI: doi.org/10.3390/ijms241310503.